

CLASSIFICATION OF REACTION TO FIRE PERFORMANCE IN ACCORDANCE WITH EN 13501-1:2007+A1:2009

Classification no.	2015-Efectis-R001026
Sponsor	Avery Dennison Graphics & Reflective Solutions P.O. Box 28 2300 AA LEIDEN THE NETHERLANDS
Product name	Avery Dennison®, MPI™ 1104 Cast series
Prepared by	Efectis Nederland BV
Notified body no.	1234
Author(s)	C.C.M. Steinhage B.Sc. E.O. van der Laan M.Sc.
Project number	ENL-15-000723
Date of issue	August 2015
Number of pages	5

1. INTRODUCTION

This classification report defines the classification assigned to **Avery Dennison®**, **MPI™ 1104 Cast series** in accordance with the procedures given in EN 13501-1:2007+A1:2009.

2. DETAILS OF CLASSIFIED PRODUCT

2.1 GENERAL

The product, **Avery Dennison®**, **MPI™ 1104 Cast series**, is defined as a wall covering.

2.2 MANUFACTURER

Avery Dennison
Graphics & Reflective Solutions
P.O. Box 28
2300 AA LEIDEN
THE NETHERLANDS

2.3 PRODUCT DESCRIPTION

According to the sponsor the product is from inside out composed of:

- Film: 50 µm gloss white cast vinyl
- Adhesive: 30 µm repositionable permanent, grey tie coat, acrylic based
- Backing paper
 - MPI 1104 Staflat liner
 - MPI 1104 EA Easy Apply liner

The product has a total thickness of approx. 80 µm and a mass per unit area of approx. 115 g/m² (measured on the product).

See also Appendix 'Product data sheet' in the test reports.

3. REPORTS, RESULTS AND CRITERIA IN SUPPORT OF THIS CLASSIFICATION

3.1 REPORTS

Name of Laboratories	Name of sponsor	Report ref. no.	Test method
Efectis Nederland BV THE NETHERLANDS	Avery Dennison Graphics & Reflective Solutions THE NETHERLANDS	2015-Efectis-R001024 2015-Efectis-R001025	EN ISO 11925-2:2010 EN 13823:2014

3.2 TEST RESULTS

Test method and test number	Parameter	No. tests	Results	
			Continuous parameter - mean (m)	Compliance with parameters
EN ISO 11925-2				
surface flame impingement	$F_s \leq 150$ mm	6	29	-
	Ignition of filter paper		-	Compliant
Edge flame Impingement	$F_s \leq 150$ mm	6	15	-
	Ignition of filter paper		-	Compliant
EN 13823				
	FIGRA _{0,2MJ} [W/s]	3	56	-
	FIGRA _{0,4MJ} [W/s]		0	-
	THR _{600s} [MJ]		0.5	-
	LFS < edge		-	Compliant
	SMOGRA [m ² /s ²]		12	-
	TSP _{600s} [m ²]		44	-
	Flaming debris - flaming ≤ 10 s - flaming > 10 s		-	Compliant Compliant

3.3 CLASSIFICATION CRITERIA

Fire classification of construction products and building elements Excluding floorings and linear pipe thermal insulation products			
Classification criteria			
Class	B	C	D
Test method(s)			
EN ISO 11925-2 Exposure = 30 s	$F_s \leq 150$ mm within 60 s Ignition of the paper in EN ISO 11925-2 results in a d2 classification.		
EN 13823	FIGRA _{0,2 MJ} ≤ 120 W/s LFS < edge of specimen THR _{600s} ≤ 7.5 MJ	FIGRA _{0,4 MJ} ≤ 250 W/s LFS < edge of specimen THR _{600s} ≤ 15 MJ	FIGRA _{0,4 MJ} ≤ 750 W/s
Additional classification			
Smoke production	s1 = SMOGRA ≤ 30 m ² /s ² and TSP _{600s} ≤ 50 m ² ; s2 = SMOGRA ≤ 180 m ² /s ² and TSP _{600s} ≤ 200 m ² ; s3 = not s1 or s2		
Flaming Droplets/particles	d0 = no flaming droplets/ particles in EN 13823 within 600 s; d1 = no flaming droplets/ particles persisting longer than 10 s in EN 13823 within 600 s; d2 = not d0 or d1.		

4. CLASSIFICATION AND FIELD OF APPLICATION

4.1 REFERENCE OF CLASSIFICATION

This classification has been carried out in accordance with clause 11 of EN 13501-1:2007+A1:2009.

4.2 CLASSIFICATION

The product, Avery Dennison®, MPI™ 1104 Cast series, in relation to its reaction to fire behaviour is classified:

B

The additional classification in relation to smoke production is:

s1

The additional classification in relation to flaming droplets / particles is:

d0

Reaction to fire classification: B - s1, d0

4.3 FIELD OF APPLICATION

This classification is valid for the following product parameters:

Thickness

- Film 50 µm
- Adhesive 30 µm

Surface density 115 g/m²

This classification is valid for the following end use applications:

Substrate Non-combustible
(class A1 according to EN 13238:2010)

Air gap 40 mm

Methods and means of fixing Glued, using the products adhesive

Joints Including joints


Other aspects of end use conditions Wall covering

4.4 DURATION OF THE VALIDITY OF THIS CLASSIFICATION REPORT

There are no limitations in time on the validity of this report.

5. LIMITATIONS

This classification document does not represent type approval or certification of the product.

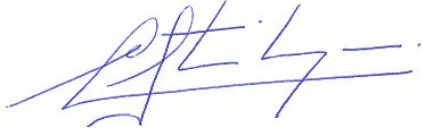

C.C.M. Steinhage B.Sc.
Project leader reaction to fire



E.O. van der Laan M.Sc.
Project leader reaction to fire